




















**Transient Temperature Results**

Figure 12 shows the measured transient temperatures at three points representing the weld toe (A), weld root (B) and corner point (C) as illustrated in Fig. 8 and the corresponding predicted transient temperatures by the present 3-D power density heat source solution. Transient temperatures are calculated using the solution obtained for double ellipsoidal distributed heat source.

The parameters of the double ellipsoids used for the calculation in this section were taken from the result obtained previously regarding the best fit of weld pool geometry ( $a_h = 10$  mm,  $b_h = 2$  mm,  $c_{hf} = 10$  mm,  $c_{hb} = 20$  mm and  $\eta = 0.85$ ), and the same heat transfer material properties were used ( $c = 600$  J/kg°C;  $k = 29$  J/m/s°C;  $\rho = 7820$  kg/m<sup>3</sup> and, therefore,  $a = k/c\rho = 6.181 \times 10^{-6}$  m<sup>2</sup>/s).


It can be seen from Fig. 12 that the measured temperatures of points A and B increased almost immediately after the welding arc passed their position. The maximum temperature of point B is higher than that of A, as expected, because B is located closer to the weld pool boundary than A. Figure 12 also shows the maximum measured transient temperature of point C is lower than that of point A and B, as expected, due to the fact that position C was much farther from the weld pool than that of A or B (about 3 mm from the weld toe). It is also worth noting here a delayed increase in temperature of point C compared with A and B, due to its particular position and the welding path, was successfully recorded. An expected transition zone in the transient temperature of point C, due

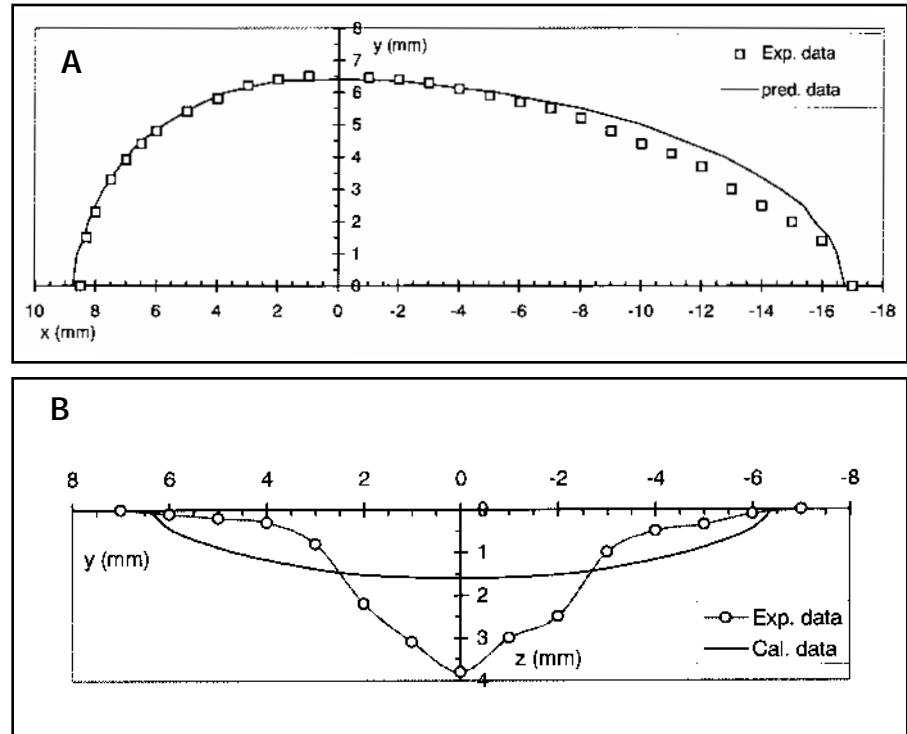


*Fig. 11 — Comparisons between calculated and measured data of the weld pool: A — Top view of the weld pool; B — longitudinal cross section.*

to its corner position, was successfully recorded, as shown in Fig. 12. Furthermore, Fig. 12 also shows there is a very good agreement between the predicted and measured transient temperatures for all three points A, B and C. The shape and the magnitude of the predicted temperatures were expected and were very close to the measured ones. The transition zone in the temperature history of corner point C due to the welding path was successfully simulated by the numerical calculation.

Figure 13 shows another set of measured temperature data compared with the one shown in Fig. 12. It can be seen from Fig. 13 the repeatability of the measured transient temperature is very good in terms of both shape and magnitude. The difference in the peak temperature at the weld toe, weld root and the corner positions is less than 100°C, which is quite acceptable for high-temperature gradients at these positions. This temperature difference also incorporated the unavoidable experimental errors in

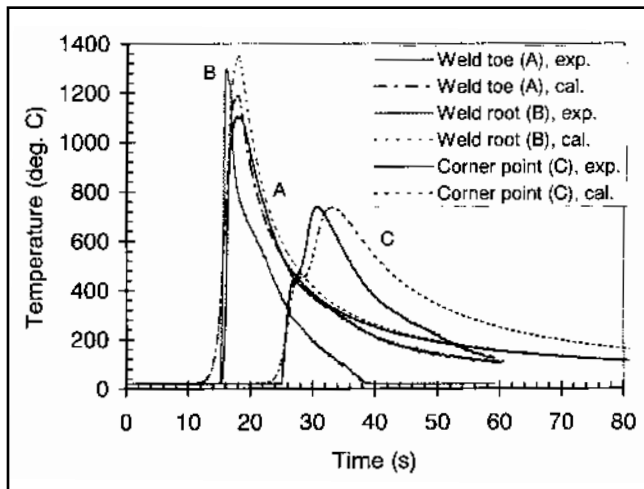

*Fig. 12 — Comparison between calculated and measured transient temperatures.*

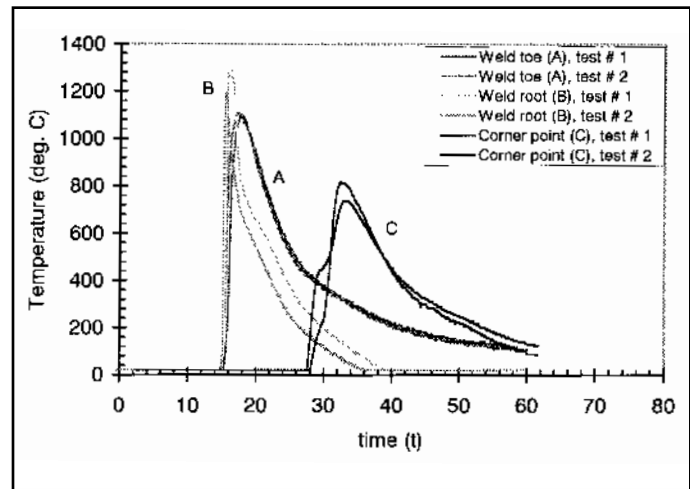

*Fig. 13 — Repeatability of the measured transient temperatures.*

